

# WSDOT Errata to FOP for AASHTO R 97

## *Sampling Asphalt Mixtures*

WAQTC FOP for AASHTO R 97 has been adopted by WSDOT with the following changes:

### **Sample Size**

For Acceptance sampling and testing only: WSDOT requires a minimum of two times the amount required for testing. This should be approximately 60 lbs.

For Acceptance and Conformation sampling and testing or for Test Section sampling and testing: WSDOT requires a minimum of four times the amount required for testing. This should be approximately 120 lbs. (See WSDOT *Construction Manual* Section 9-3.7 for Conformation sampling frequency)

**Note:** When sampling or testing for Determination of the Moving Average of Theoretical Maximum Density (TMD) for Asphalt Mixtures, please refer to WSDOT SOP 729.

### **Procedure**

#### **General**

*Include the steps below:*

- Immediately upon obtaining a sample, using a verified thermometer, check and record temperature of the sample.
- The material shall be tested to determine variations. The supplier/contractor shall sample the HMA mixture in the presence of the Project Engineer. The supplier/contractor shall provide one of the following for safe and representative sampling:
  - a. A mechanical sampling device installed between the discharge of the silo and the truck transport that is approved by the Regional Materials Engineer.
  - b. Platforms or devices to enable sampling from the truck transport without entering the truck transport for sampling Asphalt Mixtures.

**Conveyor Belts** - *Method not recognized by WSDOT.*

**Paver Auger** - *Method not recognized by WSDOT.*

**Windrow** - *Method not recognized by WSDOT.*

#### **Roadway before Compaction**

**Method 1 - Obtaining a Sample on Grade or Untreated Base (Plate Method)** - *Method not recognized by WSDOT.*

**Method 2 - Obtaining a Sample on Asphalt Surface (Non-Plate Method)** - *Method not recognized by WSDOT.*

#### **Stockpiles**

Method 1 – Loader - Method not recognized by WSDOT.

Method 2 – Stockpile Face - Method not recognized by WSDOT.



## **SAMPLING ASPHALT MIXTURES FOP FOR AASHTO R 97**

### **Scope**

This procedure covers the sampling of asphalt mixtures from plants, haul units, and roadways in accordance with AASHTO R 97-19. Sampling is as important as testing, use care to obtain a representative sample and to avoid segregation and contamination of the material during sampling.

*This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

### **Apparatus**

- Shovel or Metal Scoops, or Other Equipment: square-head metal shovels at least 125 mm (5.5 in.) wide.
- Sample containers: such as cardboard boxes, metal cans, stainless steel bowls, or other agency-approved containers
- Sampling plate: thick metal plate, minimum 8 gauge, sized to accommodate sample requirements, with a wire attached to one corner long enough to reach from the center of the paver to the outside of the farthest auger extension. A minimum of one hole 6 mm (0.25 in.) in diameter must be provided in a corner of the plate.
- Cookie cutter sampling device: formed steel angle with two 100 mm by 150 mm by 9 mm (4 in. by 6 in. by 3/8 in.) handles, sized to accommodate sample requirements. Minimum 50 mm (2 in.) smaller than the sampling plate when used together.

*Example:* Sampling plate 380 mm (15 in.) square and a cookie cutter sampling device 330 mm (13 in.) square.

- Mechanical sampling device: a permanently attached device that allows a sample receptacle to pass perpendicularly through the entire stream of material or diverts the entire stream of material into the container by manual, hydraulic, or pneumatic operation.
- Release agent: a non-stick product that prevents the asphalt mixture from sticking to the apparatus and does not contain solvents or petroleum-based products that could affect asphalt binder properties.

### **Sample Size**

Sample size depends on the test methods specified by the agency for acceptance. Check agency requirement for the size required.

## Procedure

### General

- Select sample locations using a random or stratified random sampling procedure, as specified by the agency. The material shall be tested to determine variations. The supplier/contractor shall provide equipment for safe and appropriate sampling, including sampling devices on plants when required.
- Ensure the container(s) and sampling equipment are clean and dry before sampling.
- For dense graded mixture samples use cardboard boxes, stainless steel bowls or other agency-approved containers.
- For hot open graded mixture samples use stainless steel bowls. Do not put open graded mixture samples in boxes until they have cooled to the point that asphalt binder will not migrate from the aggregate.

### Attached Sampling Devices

These are normally permanently attached devices that allow a sample container to pass perpendicularly through the entire stream of material. Operation may be hydraulic, pneumatic, or manual and allows the sample container to pass through the stream twice, once in each direction, without overfilling. A sampling device may also divert the entire stream into a sampling receptacle.

1. Lightly coat the container attached to the sampling device with an agency-approved release agent or preheat it, or both, to approximately the same discharge temperature of the mix.
2. Pass the container twice through the material perpendicularly without overfilling the container.
3. Transfer the asphalt mixture to an agency-approved container without loss of material.
4. Repeat until proper sample size has been obtained.
5. Combine the increments to form a single sample.

### Conveyor Belts

1. Avoid sampling at the beginning or end of an asphalt mixture production run due to the potential for segregation.
2. Stop the belt containing asphalt mixture.
3. Set the sampling template into the asphalt mixture on the belt, avoiding intrusion by adjacent material.
4. Remove the asphalt mixture from inside the template, including all fines, and place in a sample container.
5. Repeat, obtaining equal size increments, until proper sample size has been obtained.
6. Combine the increments to form a single sample.

### Haul Units

1. Visually divide the haul unit into approximately four equal quadrants.
2. Identify one sampling location in each quadrant.
3. Dig down and remove approximately 0.3 m (1 ft.) of material to avoid surface segregation. Obtain each increment from below this level.
4. Combine the increments to form a sample of the required size.


### Paver Auger

1. Obtain samples from the end of the auger using a square head shovel.
2. Place the shovel in front of the auger extension, with the shovel blade flat upon the surface to be paved over.
3. Allow the front face of the auger stream to cover the shovel with asphalt mixture, remove the shovel before the auger reaches it by lifting as vertically as possible.
4. Place asphalt mixture in a sample container.
5. Repeat until proper sample size has been obtained.
6. Combine the increments to form a sample of the required size.


*Note 1:* First full shovel of material may be discarded to preheat and 'butter' the shovel.

### Windrow

1. Obtain samples from the windrow of a transport unit. Avoid the beginning or the end of the windrow section.
2. Visually divide the windrow into approximately three equal sections.
3. Remove approximately 0.3 m (1 ft) from the top of each section.
4. Fully insert the shovel into the flat surface as vertically as possible, exclude the underlying material, roll back the shovel and lift the material slowly out of the windrow to avoid material rolling off the shovel.
5. Place in a sample container.
6. Repeat, obtaining equal size increments, in each of the remaining thirds.
7. Combine the increments to form a sample of the required size.

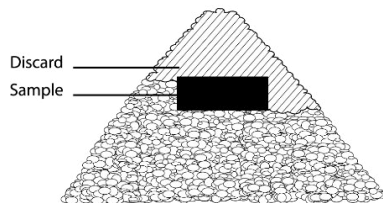

Windrow cross section

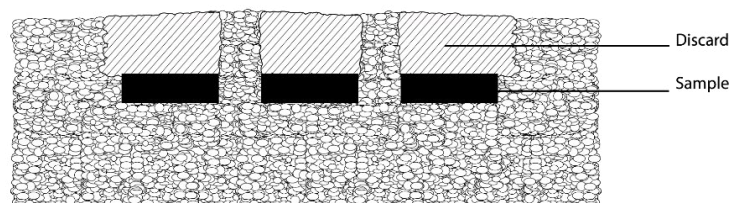

Windrow side view

### Roadway before Compaction

There are two conditions that will be encountered when sampling asphalt mixtures from the roadway before compaction. The two conditions are:

- Laying asphalt mixture on grade or untreated base material requires Method 1.
- Laying asphalt mixture on existing asphalt or laying a second lift of asphalt mixture requires Method 2.

### SAFETY:

Sampling is performed behind the paving machine and in front of the breakdown roller. For safety, the roller must remain at least 3 m (10 ft.) behind the sampling operation until the sample has been taken and the hole filled with loose asphalt mixture.

Method 1 requires a plate to be placed in the roadway in front of the paving operation and therefore there is always concern with moving, operating equipment. It is safest to stop the paving train while a plate is installed in front of the paver. When this is not possible the following safety rules must be followed.

1. The plate placing operation must be at least 3 m (10 ft.) in front of the paver or pickup device. The technician placing the plate must have eye contact and communication with the paving machine operator. If eye contact cannot be maintained at all time, a third person must be present to provide communication between the operator and the technician.
2. No technician is to be between the asphalt supply trucks and the paving machine. The exception to this rule is if the supply truck is moving forward creating a windrow, in which case the technician must be at least 3 m (10 ft.) behind the truck.

If at any time the Engineer feels that the sampling technique is creating an unsafe condition, the operation is to be halted until it is made safe or the paving operation will be stopped while the plate is being placed.

### Method 1 - Obtaining a Sample on Grade or Untreated Base (Plate Method)

1. Following the safety rules detailed above, the technician is to:
  - a. Smooth out a location in front of the paver at least 0.5 m (2 ft.) inside the edge of the mat.
  - b. Lay the plate down diagonally with the direction of travel, keeping it flat and tight to the base with the lead corner facing the paving machine.

*Note 2:* The plate may be secured by driving a nail through the hole in the lead corner of the plate.

2. Pull the wire, attached to the outside corner of the plate, taut past the edge of the asphalt mixture mat and secure it. Let the paving operation pass over the plate and wire.
3. Using the exposed end of the wire, pull the wire up through the fresh asphalt mixture to locate the corner of the plate.

- a. Plate only:
  - i. Using a small square head shovel or scoop, or both, remove the full depth of the asphalt mixture from the plate. Take care to prevent sloughing of adjacent material.
  - ii. Place asphalt mixture, including any material adhering to the plate and scoop or shovel in a sample container.
- b. "Cookie Cutter":
  - i. Place the "cookie cutter" sample device, just inside the end of the wire; align the cutter over the plate. Press "cookie cutter" device down through the asphalt mixture to the plate.
  - ii. Using a small square tipped shovel or scoop, or both, carefully remove all the asphalt mixture from inside of the cutter and place in a sample container.
  - iii. Remove the sample cutter and the plate from the roadway. The hole made from the sampling must be filled by the contractor with loose asphalt mixture.

### **Method 2 - Obtaining a Sample on Asphalt Surface (Non-plate Method)**

1. After the paving machine has passed the sampling point, immediately place the "cookie cutter" sampling device on the location to be sampled.
2. Push the cutter down through the asphalt mixture until it is flat against the underlying asphalt mat.
3. Using a small square tipped shovel or scoop, or both, carefully remove all the asphalt mixture from inside of the cutter and place in a sample container.
4. Remove the cutter from the roadway. The hole made from the sampling must be filled by the contractor with loose asphalt mixture.

### **Stockpiles**

Remove at least 0.1 m (4 in.) from the surface before sampling; mixtures in a stockpile may develop an oxidized crust.


#### **Method 1 – Loader**

1. Direct the loader operator to enter the stockpile with the bucket at least 0.3 m (1 ft) above ground level without contaminating the stockpile.
2. Obtain a full loader bucket of the asphalt mixture; tilt the bucket back and up.
3. Form a small sampling pile at the base of the stockpile by gently rolling the asphalt mixture out of the bucket with the bucket just high enough to permit free-flow of the mixture. Repeat as necessary.
4. Create a flat surface by having the loader "back-drag" the small pile.

5. Obtain approximately equal increments from at least three randomly selected locations on the flat surface at least 0.3 m (1 ft) from the edge.
6. Fully insert the shovel, exclude the underlying material, roll back the shovel and lift the asphalt mixture slowly out of the pile to avoid mixture rolling off the shovel.
7. Combine the increments to form a sample.

### Method 2 – Stockpile Face

1. Create horizontal surfaces with vertical faces in the top, middle, and bottom third of the stockpile with a shovel or a loader if one is available.
2. Shove a flat board against the vertical face behind the sampling location to prevent sloughing of asphalt mixture. Discard the sloughed mixture to create the horizontal surface.
3. Obtain the sample from the horizontal surface as close as possible to the intersection of the horizontal and vertical faces.
4. Obtain at least one sample increment of equal size from each of the top, middle, and bottom thirds of the pile.
5. Combine the increments to form a single sample.

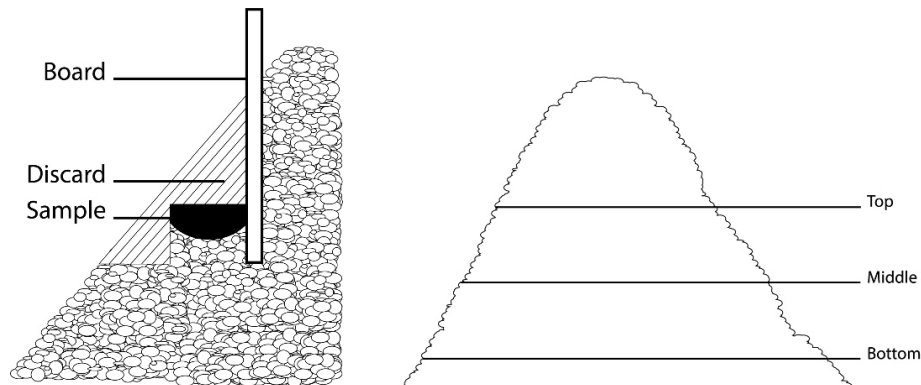

### Identification and Shipping

1. Identify sample containers as required by the agency.
2. Ship samples in containers that will prevent loss, contamination, or damage.



---

ASPHALT

WAQTC

FOP AASHTO R 97 (20)

**Report**

- On forms approved by the agency
- Sample ID
- Date
- Time
- Location
- Quantity represented

ASPHALT

WAQTC

FOP AASHTO R 97 (20)

**PERFORMANCE EXAM CHECKLIST**

**SAMPLING ASPHALT MIXTURES  
FOP FOR AASHTO R 97**

Participant Name \_\_\_\_\_ Exam Date \_\_\_\_\_

**Record the symbols “P” for passing or “F” for failing on each step of the checklist.**

| <b>Procedure Element</b>   | <b>Trial 1</b> | <b>Trial 2</b> |
|--|----------------|----------------|
| <b>Attached Sampling Device</b>  |                |                |
| 1. Container coated or preheated or both?                                  | _____          | _____          |
| 2. Sampling device passed through stream twice perpendicular to material?  | _____          | _____          |
| 3. Sampling device not over filled?  | _____          | _____          |
| <b>Conveyor Belt</b>   |                |                |
| 4. Belt stopped?   | _____          | _____          |
| 5. Sampling template set on belt, avoiding intrusion of adjacent material? | _____          | _____          |
| 6. Sample, including all fines, scooped off?                               | _____          | _____          |
| <b>Haul Units</b>  |                |                |
| 7. Unit divided into four quadrants?                                       | _____          | _____          |
| 8. Increment obtained from each quadrant, 0.3 m (1ft.) below surface?      | _____          | _____          |
| 9. Increments combined to make up the sample?                              | _____          | _____          |
| <b>Paver Auger</b>   |                |                |
| 10. Shovel blade flat on the surface to be paved?                          | _____          | _____          |
| 11. Shovel lifted vertically after it is filled?                           | _____          | _____          |
| <b>Windrow</b>   |                |                |
| 12. Beginning and end avoided?   | _____          | _____          |
| 13. Equal increments obtained from three sections?                         | _____          | _____          |
| 14. Approximately 0.3 m (1 ft) removed from top of each section?           | _____          | _____          |
| 15. Underlying material excluded?  | _____          | _____          |
| <b>Roadway Before Compaction (Method 1)</b>                                |                |                |
| 16. Plate placed well in front of paver?                                   | _____          | _____          |
| 17. Wire pulled to locate plate corner?                                    | _____          | _____          |

**OVER**

**Procedure Element**

**Trial 1    Trial 2**

18. Cookie cutter (if used) placed on asphalt and pushed through to plate? \_\_\_\_\_

19. All material removed from inside the cutter? \_\_\_\_\_

**Roadway Before Compaction (Method 2)**

20. Cookie cutter placed on asphalt and pushed through to underlying material? \_\_\_\_\_

21. All material removed from inside the cutter? \_\_\_\_\_

**Stockpile Method 1– (Loader sampling)**

22. Loader operator directed to enter the stockpile with the bucket at least 0.3 m (1 ft) above ground level without contaminating the stockpile? \_\_\_\_\_

23. The loader obtained a full loader bucket of the material with the bucket tilted back and up? \_\_\_\_\_

24. A small sampling pile formed at the base of the stockpile by gently rolling the material out of the bucket with the bucket just high enough to permit free-flow of the material? \_\_\_\_\_

25. A flat surface created by the loader back dragging the small pile? \_\_\_\_\_

26. Increment sampled from three locations at least 0.3 m (1 ft) from the edge by fully inserting the shovel into the flat pile as vertically as possible, care taken to exclude the underlying material? \_\_\_\_\_

**Stockpile Method 2 (Stockpile Face)**

27. Created horizontal surfaces with vertical faces? \_\_\_\_\_

28. Sample obtained from the horizontal face as close as possible to the vertical face? \_\_\_\_\_

29. At least one increment taken from each of the top, middle, and bottom thirds of the stockpile? \_\_\_\_\_

**General**

30. Sample placed in appropriate container? \_\_\_\_\_

31. Sample size meets agency requirements? \_\_\_\_\_

32. Sample identified as required? \_\_\_\_\_

Comments:      First attempt:    Pass \_\_\_\_\_ Fail \_\_\_\_\_      Second attempt:    Pass \_\_\_\_\_ Fail \_\_\_\_\_

\_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_  
\_\_\_\_\_

**Examiner Signature** \_\_\_\_\_

**WAQTC #:** \_\_\_\_\_

ASPHALT

WAQTC

FOP AASHTO R 97 (19)

**PERFORMANCE EXAM CHECKLIST (ORAL)****SAMPLING ASPHALT MIXTURES  
FOP FOR AASHTO R 97**

Participant Name \_\_\_\_\_ Exam Date \_\_\_\_\_

Record the symbols "P" for passing or "F" for failing on each step of the checklist.

| Procedure Element  | Trial 1 | Trial 2 |
|--|---------|---------|
| <b>1. At the hot plant, how must a sample be obtained using an attached sampling device?</b> |         |         |
| a. Coat or preheat sample container.   | _____   | _____   |
| b. Sampling device passed through stream twice perpendicular to material.                    | _____   | _____   |
| c. The sampling device cannot be overfilled.   | _____   | _____   |
| <b>2. How is a sample obtained from a conveyor belt?</b>                                     |         |         |
| a. Stop the belt.  | _____   | _____   |
| b. Set the sampling template on belt, avoiding intrusion of adjacent material.               | _____   | _____   |
| c. All the material is removed from belt including all fines.                                | _____   | _____   |
| <b>3. What must be done to sample from transport units?</b>                                  |         |         |
| a. Divide the unit into four quadrants.  | _____   | _____   |
| b. Obtain increments from each quadrant, 0.3 m (1 ft) below surface.                         | _____   | _____   |
| <b>4. How is a sample obtained from the paver auger?</b>                                     |         |         |
| a. Shovel blade is placed flat on the surface to be paved in front of the auger extension?   | _____   | _____   |
| b. Shovel is filled and removed by lifting as vertically as possible?                        | _____   | _____   |
| <b>5. Describe the procedure for sampling from a windrow.</b>                                |         |         |
| a. Do not sample from the beginning or end of the windrow.                                   | _____   | _____   |
| b. Approximately 0.3 m (1 ft) removed from the top.  | _____   | _____   |
| c. Underlying material is excluded   | _____   | _____   |
| d. Equal increments obtained from 3 locations along the windrow.                             | _____   | _____   |

OVER

**Procedure Element**

**Trial 1 Trial 2**

**6. Describe how to take samples from the roadway using Method 1 (plate).**

- a. Place the plate well in front of the paver. \_\_\_\_\_
- b. Pull the wire to locate the corner of the plate. \_\_\_\_\_
- c. Place the cutter (if used) on the asphalt material above the plate and push it down to the plate. \_\_\_\_\_
- d. Collect all the material inside the cutter. \_\_\_\_\_

**7. Describe how to take samples from the roadway using Method 2.**

- a. Place the cutter on the asphalt material and push it down to the underlying material. \_\_\_\_\_
- b. Collect all the material inside the cutter. \_\_\_\_\_

**8. Describe the procedure for sampling a stockpile Method 1 (Loader Sampling).**

- a. Loader removes surface and creates sampling pile. \_\_\_\_\_
- b. Loader back drags pile to create a flat surface. \_\_\_\_\_
- c. Take three approximately equal increments from at least 0.3 m (1 ft) from the edge, excluding the underlying material. \_\_\_\_\_

**9. Describe the procedure for sampling a stockpile Method 2 (Stockpile Face Sampling).**

- a. Create horizontal surfaces with vertical faces with a shovel. \_\_\_\_\_
- b. At least one increment taken from each of the top, middle, and bottom thirds of the stockpile. \_\_\_\_\_

**10. Increments combined to form a sample of required size?**

\_\_\_\_\_

**11. What types of containers can be used?**

- a. Cardboard boxes, stainless steel bowls, or other agency approved containers. \_\_\_\_\_

**12. What dictates size of sample?**

- a. Agency requirements. \_\_\_\_\_
- b. Specified by test method. \_\_\_\_\_

Comments: First attempt: Pass \_\_\_\_\_ Fail \_\_\_\_\_ Second attempt: Pass \_\_\_\_\_ Fail \_\_\_\_\_

\_\_\_\_\_

\_\_\_\_\_

\_\_\_\_\_

\_\_\_\_\_

Examiner Signature \_\_\_\_\_

WAQTC #: \_\_\_\_\_